

---

## Radiation Hardened Plastic Production and QCI Flow

---

This document outlines the production flow and lot assurance testing for the Renesas Radiation Hardened Plastic Products for space applications. In general, this applies to products with part numbers ISL7xxxxSLHM and ISL7xxxxSEHM. See the datasheet for each individual device for more information specific to each device.

### Contents

<b>1. Radiation Hardened Plastic Production Testing</b> .....	<b>2</b>
<b>2. Radiation Hardened Plastic Lot Acceptance Testing</b> .....	<b>4</b>
2.1 Preconditioning .....	4
2.2 Sampling Requirements .....	4
2.3 Radiation Lot Assurance Testing .....	5
<b>3. Revision History</b> .....	<b>6</b>

# 1. Radiation Hardened Plastic Production Testing

This section outlines the production flow that 100% of the radiation hardened plastic products receive. This testing flow aligns with industry accepted standards including SAE AS6294/1 and NASA PEMS-INST-001.



Figure 1. Flow Chart

Table 1. Radiation Hardened Plastic Production Test Flow Screening

Test	Test Method Used	Notes
Initial Electrical Test	Per device specification (Datasheet), Read and Record	Test performed at nominal operating temperature (25°C), and the minimum and maximum rated temperatures
Laser Serialization	MIL-STD-1580 for PEMs	
Radiography	MIL-STD-1580 for PEMs	
Acoustic Microscopy	J-STD-020, J-STD-035	Includes 4hr post-Bake 125°C
Temperature Cycling	MIL-STD-883, Method 1010	20 cycles, -65 to 150°C
Electrical Test	Per device specification (Datasheet), Read and Record	Test performed at nominal operating temperature (25°C)
Dynamic Burn-in	MIL-STD-883, Method 1015 for Class S	BI test performed at +135°C
Post Dynamic Burn-in Electrical Test	Per device specification, Read and Record	Test performed at 25°C
Static Burn-in test	MIL-STD-883, Method 1015 for Class S	BI test performed at +135°C
Final Parametric and Functional Electrical Test	Per device specification, Read and Record	Test performed at nominal operating temperature (25°C), and the minimum and maximum rated temperatures, delta analysis for PDA performed at 25°C only
Calculate Percent Defective	Maximum Acceptable PDA, based on 25°C delta analysis	<5%
Radiography	MIL-STD-1580 for PEMs	
Acoustic Microscopy	J-STD-020, J-STD-035	Includes 4hr post-Bake 125°C
Select Samples for Lot Assurance Testing		See below for sample size selection criteria
Coplanarity Screening, External Visual, Packaging	MIL-STD-1580 for PEMs	

## 2. Radiation Hardened Plastic Lot Acceptance Testing

When units have gone through the production test flow outlined in the previous section, the products enter lot acceptance testing. These screenings are done on a lot-by-lot basis. For package related stresses, Subgroups 2 and 3 in the flowchart are intended to ensure that the package is reliably built and no defects exist. Subgroup 1 testing is intended to show any early life failures because of the die or wafer processing.

Lastly, radiation lot acceptance testing is performed per the device specification. The radiation test samples are not included in any of the subgroup testing and they are selected directly after completing the production flow.

### 2.1 Preconditioning

All samples selected for lot acceptance testing are exposed to a pre-conditioning step. Preconditioning consists of the following:

1. Precondition bake at 125°C +5°/-0°C for 4 hours minimum
2. Moisture Soak
  - a. MSL 1 85°C, 85%RH 168 hours
  - b. MSL 2 85°C, 60%RH 168 hours
  - c. MSL 3 30°C, 60%RH 192 hours
3. SMT Device Reflow Simulation

### 2.2 Sampling Requirements

Lot Acceptance Test(s)	Samples Required Based on Lot Size					
	Lot Size	40–60	61–120	121–240	241–500	>500
Total Samples Required (All samples go through Precondition Bake, Moisture Soak, SMT Reflow Simulation, and C-SAM)		36(0)	48(0)	69(0)	96(0)	135(0)
Subgroup 1 (Life test)		12(0)	16(0)	23(0)	32(0)	45(0)
Subgroup 2 (Biased HAST)		12(0)	16(0)	23(0)	32(0)	45(0)
Subgroup 3 (Temp Cycle)		12(0)	16(0)	23(0)	32(0)	45(0)
Radiation Testing		4(0)	4(0)	4(0)	4(0)	4(0)

### 2.3 Radiation Lot Assurance Testing

Samples for radiation lot assurance testing are selected from material that has undergone the production test flow. There are four samples per wafer lot tested. This testing qualifies the entire wafer lot for total ionizing dose radiation per the datasheet specification on a given part.

This section outlines the lot assurance testing that the radiation hardened plastic products receive with sampling requirements outlined in [Sampling Requirements](#). This testing flow aligns with industry accepted standards including SAE AS6294/1 and NASA PEMS-INST-001

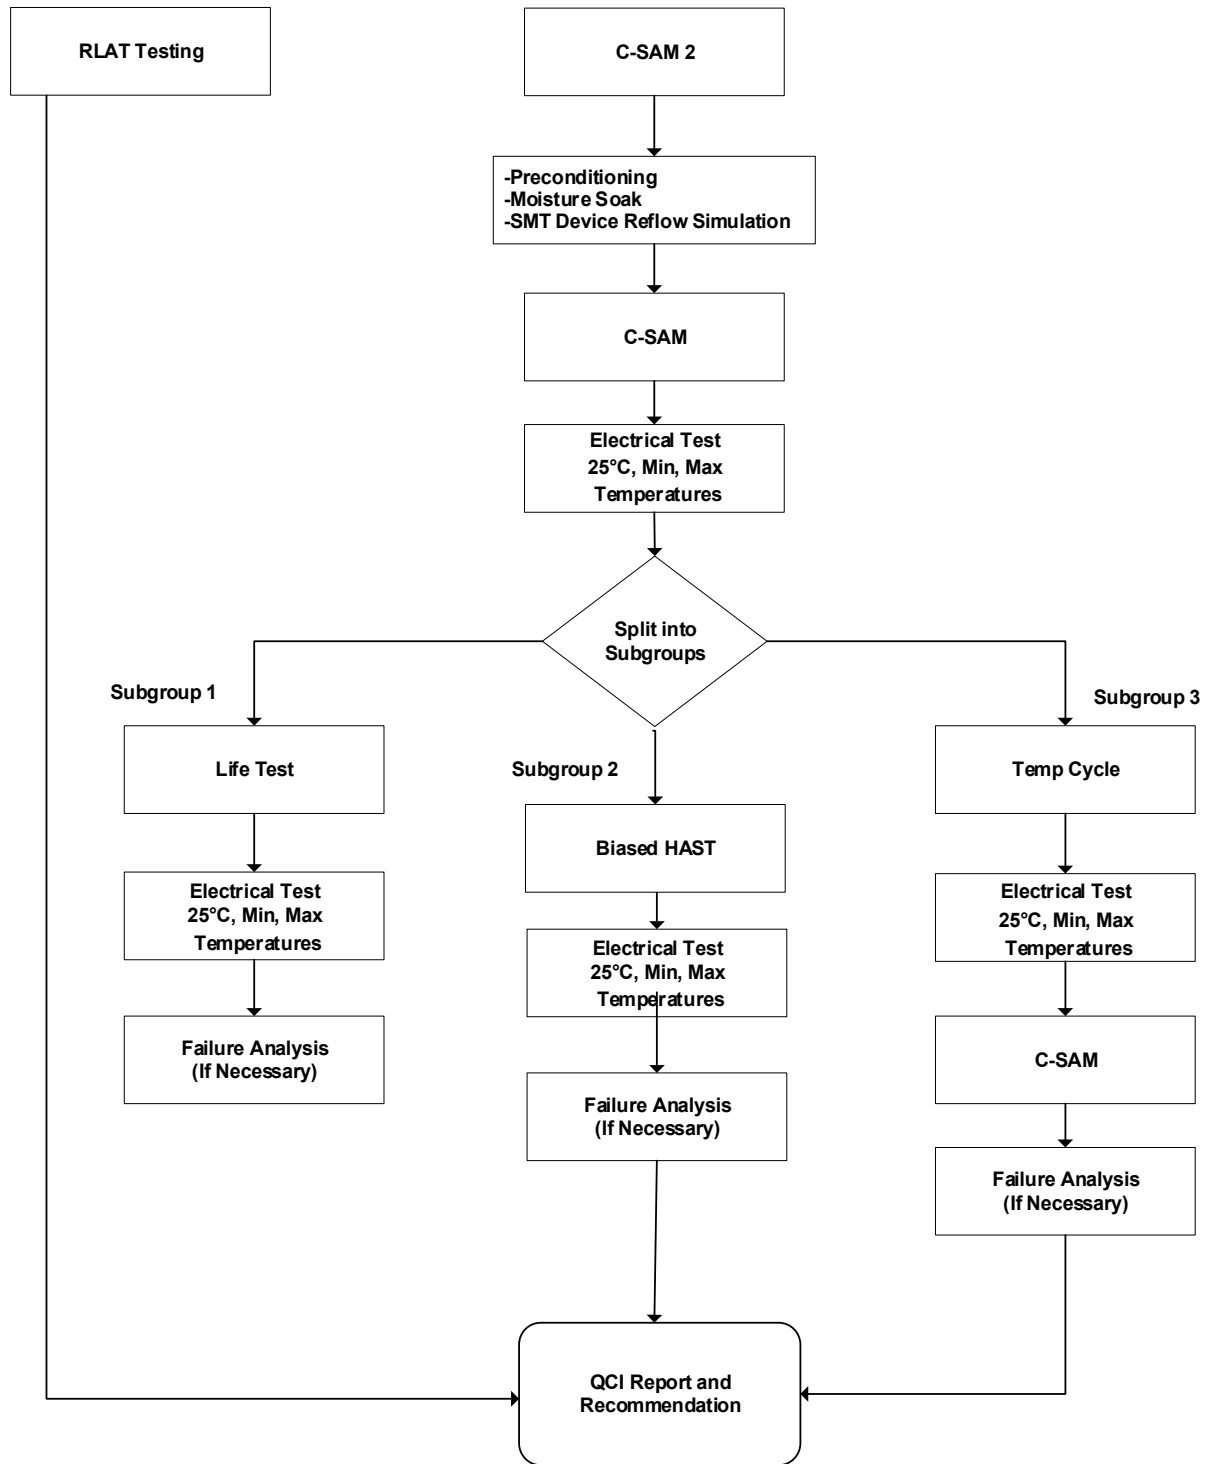


Figure 2. Flow Chart for Lot Acceptance Testing of Palm Bay PEMS Products

**Table 2. Flow Table for Lot Acceptance Testing of Palm Bay PEMS Products**

Test	Sub Test	Test Method and Conditions
Radiation Analysis		MIL-STD-883 TM 1019
External Visual Inspection		MIL-STD-1580 for PEMS
Preconditioning	Moisture Soak	JESD22-A113 paragraph 4.5 per applicable moisture sensitivity level (MSL) per J-STD-020
	SMT Devices Reflow Simulation (with flux application, cleaning, and drying)	JESD22-A113, paragraph 4.6 through 4.9. Peak solder reflow temperature +235°C
	Through-hole devices Resistance to soldering temperature	JESD22-B106
Acoustic Microscopy (C-SAM)	All parts	J-STD-020, J-STD-035 Includes 4hr post-Bake 125°C
Electrical Measurements	Per device specification, Read and Record	Measure at 25°C, minimum and maximum rated temperatures
Life Test Subgroup 1	High Temperature Operational Life Testing (HTOL)	MIL-STD-883, Method 1005, Condition D $T_A = 125^\circ\text{C}$ , 2000hrs minimum or $T_A = 135^\circ\text{C}$ , 1600hrs minimum
	Electrical measurements (per device specification, Read and Record)	Measure at 25C, minimum and maximum rated temperatures
Highly Accelerated Stress Test (HAST) Subgroup 2	Biased HAST	JESD22-A110 with continuous bias (96hrs, +130C, 85% RH).
	Electrical measurements (per device specification, Read and Record)	Measure at 25C, minimum and maximum rated temperatures
Temperature Cycling Subgroup 3	Temperature Cycling	MIL-STD-883, Method 1010 Condition C, -65C to 150C, 500 cycles minimum
	Electrical measurements (per device specification, Read and Record)	Measure at 25°C, minimum and maximum rated temperatures
	Acoustic Microscope inspection (C-SAM)	J-STD-020, J-STD-035

### 3. Revision History

Revision	Date	Description
1.03	Jun 2, 2023	Updated Table 2.
1.02	Feb 16, 2022	Updated description on page 1.
1.01	Apr 12, 2021	Corrected two typos. Updated Figure 2
1.00	Apr 7, 2021	Initial release.

## IMPORTANT NOTICE AND DISCLAIMER

RENESAS ELECTRONICS CORPORATION AND ITS SUBSIDIARIES (“RENESAS”) PROVIDES TECHNICAL SPECIFICATIONS AND RELIABILITY DATA (INCLUDING DATASHEETS), DESIGN RESOURCES (INCLUDING REFERENCE DESIGNS), APPLICATION OR OTHER DESIGN ADVICE, WEB TOOLS, SAFETY INFORMATION, AND OTHER RESOURCES “AS IS” AND WITH ALL FAULTS, AND DISCLAIMS ALL WARRANTIES, EXPRESS OR IMPLIED, INCLUDING, WITHOUT LIMITATION, ANY IMPLIED WARRANTIES OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE, OR NON-INFRINGEMENT OF THIRD PARTY INTELLECTUAL PROPERTY RIGHTS.

These resources are intended for developers skilled in the art designing with Renesas products. You are solely responsible for (1) selecting the appropriate products for your application, (2) designing, validating, and testing your application, and (3) ensuring your application meets applicable standards, and any other safety, security, or other requirements. These resources are subject to change without notice. Renesas grants you permission to use these resources only for development of an application that uses Renesas products. Other reproduction or use of these resources is strictly prohibited. No license is granted to any other Renesas intellectual property or to any third party intellectual property. Renesas disclaims responsibility for, and you will fully indemnify Renesas and its representatives against, any claims, damages, costs, losses, or liabilities arising out of your use of these resources. Renesas' products are provided only subject to Renesas' Terms and Conditions of Sale or other applicable terms agreed to in writing. No use of any Renesas resources expands or otherwise alters any applicable warranties or warranty disclaimers for these products.

(Disclaimer Rev.1.0 Mar 2020)

### Corporate Headquarters

TOYOSU FORESIA, 3-2-24 Toyosu,  
Koto-ku, Tokyo 135-0061, Japan  
[www.renesas.com](http://www.renesas.com)

### Contact Information

For further information on a product, technology, the most up-to-date version of a document, or your nearest sales office, please visit:  
[www.renesas.com/contact/](http://www.renesas.com/contact/)

### Trademarks

Renesas and the Renesas logo are trademarks of Renesas Electronics Corporation. All trademarks and registered trademarks are the property of their respective owners.